

Face-Centered-Cubic B₈₀ Metal: Density functional theory calculations

Qing-Bo Yan, Qing-Rong Zheng, and Gang Su*

College of Physical Sciences, Graduate University of Chinese Academy of Sciences, P.O. Box 4588, Beijing 100049, China

By means of *ab initio* calculations within the density functional theory, we have found that B₈₀ fullerenes can condense to form stable face-centered-cubic (fcc) solids. It is shown that when forming a crystal, B₈₀ cages are geometrically distorted, the I_h symmetry is lowered to T_h , and four boron-boron chemical bonds are formed between every two nearest neighbor B₈₀ cages. The cohesive energy of B₈₀ fcc solid is 0.23 eV/atom with respect to the isolated B₈₀ fullerene. The calculated electronic structure reveals that the fcc B₈₀ solid is a metal. The predicted solid phase would constitute a new form of pure boron, and might have diverse implications. In addition, a simple electron counting rule is proposed, which could explain the stability of B₈₀ fullerene and the recently predicted stable boron sheet.

PACS numbers: 81.05.Tp, 61.50.Ah, 71.20.Tx, 74.10.+v

Boron and carbon, the neighbors in the periodic table, both possess very rich physical and chemical properties. Carbon forms the backbone of life, as there are millions organic compounds that contain carbon in nature. Besides the graphite and diamond, carbon also possesses new isomorphics, such as carbon nanotube and fullerenes [1, 2], which have been extensively studied, and may be the fundamental materials for molecular electronics. Boron has a variety of complex isomorphous structures, such as α -rhombohedral B₁₂, β -rhombohedral B₁₀₅, and tetragonal B₅₀, etc (see e.g. [3] for review). The boron solids are usually band insulators or semiconductors [4, 5, 6], but they could become metals or superconductors under high pressure [7, 8, 9]. In the past decade, boron sheet, cluster and boron nanotube (BNT) also gain wide attention [10, 11, 12, 13, 14], most of which were shown to be metallic, and they are expected to have broad applications in various circumstances.

Recently, a new allotropic form of boron, B₈₀, with a round, monoelemental, and hollow structure, has been predicted [15], which is coined as boron fullerene. It consists of 80 boron atoms, and is very similar in shape to C₆₀ fullerene except that an additional boron atom sits in the center of each hexagon (Fig. 1(a)). B₈₀ could be one of the most stable boron cages so far [16], which, if confirmed experimentally, should be the second example of a monoelemental buckyball after C₆₀ in nature. Our further analyses indicate that B₈₀ fullerene is probably formed by multi-center deficient-electron bonds, and satisfies a simple electron counting rule. This rule could also apply to explain the outstanding stability of the new class of boron sheets and nanotubes composed of triangles and hexagons predicted recently [17, 18]. On the other hand, recall that soon after discovery of C₆₀, people found that C₆₀ clusters can condense to form solid phases such as simple cubic (sc), face-centered-cubic (fcc) [19], and hexagonal-close-packed (hcp) [20] crystals. As B₈₀ cluster has a geometrical structure similar to C₆₀, and boron and carbon share some similarities in chemistry [21], analogously, it would be natural to anticipate that the boron fullerenes could also condense to form solid phases. Here we show that, based on the *ab initio* calculations within the density functional theory (DFT) [22], B₈₀ clusters can indeed condense to form a stable fcc solid

that has a metallic electronic structure, in contrast to either the popular solid phases of pure boron that are usually insulating or semiconducting, or the fcc and hcp C₆₀ that are band insulators [23]. In addition, we find that, unlike the case of C₆₀ where the cage structure retains intact and is condensed by van der Waals force in solids [19, 24], when B₈₀ clusters condense to form the solid phase, the geometrical structure of B₈₀ is strikingly distorted [Fig. 1(d)], which is resulted from the formation of four boron-boron chemical bonds between every two nearest neighbor B₈₀ clusters. The total energy of B₈₀ fcc solid is 0.23 eV/atom lower than the isolated B₈₀ fullerene, and 0.35 eV/atom higher than α -rhombohedral B₁₂ solid. Therefore, if the fcc B₈₀ metal is eventually confirmed experimentally, it would compose a new form of pure boron in nature.

Our calculations are mainly performed by means of the ABINIT package [25]. This package is coded within the DFT framework based on pseudopotentials and plane waves, which relies on an efficient fast Fourier transform algorithm [26] for the conversion of wave functions between real and reciprocal spaces, on the adaptation to a fixed potential of the band-by-band conjugate gradient method [27], and on a potential-based conjugate-gradient algorithm for the determination of the self-consistent potential [28, 29, 30]. Troullier-Martins norm conserving pseudopotentials [31] generated by fhi98PP code [32] are applied to mimic the electron-ion interaction, and the Perdew-Wang 92 [33] exchange-correlation potential within local density approximation (LDA) [34] is used. The kinetic energy cutoff in the plane-wave basis is taken as 25 Hartree, and the tolerance for absolute differences of the total energy is set as 10^{-6} Hartree.

The structure of the isolated B₈₀ cluster is optimized in a cubic supercell with a lattice parameter 25 Å by the Broyden-Fletcher-Goldfarb-Shanno (BFGS) minimization [35] with a convergence tolerance of 10^{-5} Hartree/Bohr. As shown in Fig. 1(a), B₈₀ cluster, bearing I_h symmetry, is similar in shape to C₆₀, but there is an additional B atom centering in each hexagon, in agreement with the early calculation [15]. Apparently, a pure two-center two-electron (2c2e) bonding scheme could not give a proper description of B₈₀ fullerene, as in which each boron atom has five or six nearest neighbors

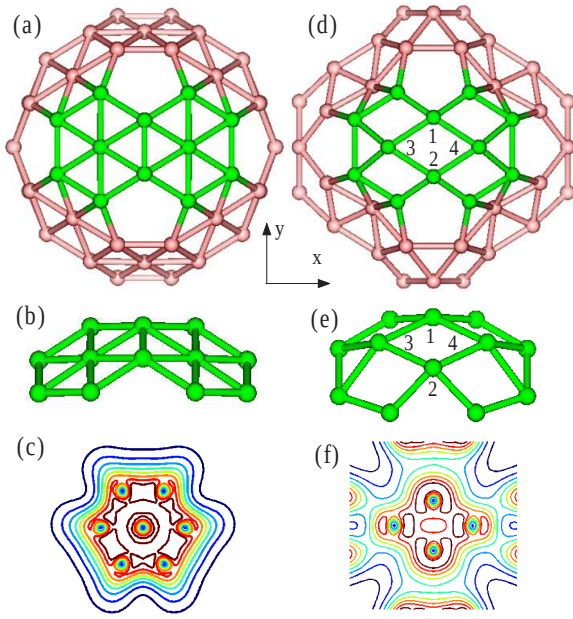


FIG. 1: (Color online) (a) Schematic structure of an isolated B_{80} cluster; (b) is the view of green (dark) parts (a pair of neighbor hexagons) in (a) after a $\pi/6$ rotation around the x axis; (c) the contour map of valence electron density in the plane of a hexagon in (b); (d) the distorted structure of B_{80} in the fcc solid; (e) is the view of green (dark) parts in (d) after a $\pi/6$ rotation around the x axis, showing the distortion of a pair of neighbor hexagons in (b); (f) the contour map of valence electron density in the plane of the rhombus, which is composed of the atoms marked by number 1-4 in (e). The red and blue colors in (c) and (f) represent high and low electron densities, respectively. (See the color bar in Fig. 2.)

but it only possesses three valence electrons. We believe that the picture of the multi-center deficient-electron bonding [36] may apply to the present case. One may note that a hexagon with an additional boron atom sitting in the center can be viewed as a group of six triangles. A B_{80} fullerene consists of 20 such hexagons and 12 pentagon holes, or equivalently, 120 triangles and 12 pentagon holes. Suppose that three boron atoms on the vertices of a triangle share a three-center two-electron (3c2e) bond. Then, a triangle would consume two electrons. As there are 120 triangles in B_{80} , 240 electrons are demanded for bondings. While the boron atoms on the vertices of pentagon holes have been counted in the triangles, no electron is consumed for pentagon holes. Thus, the total number of demanded electrons is 240, which is just equal to the total number of electrons that B_{80} possesses. Based on the multi-center deficient-electron bonding picture, such a simple electron counting method may be generalized as follows: in a stable boron quasiplanar structure (sheet, nanotube, fullerene, etc.) composed by triangles and pentagon (hexagon) holes, if we assume that each triangle consumes two electrons, while pentagon (hexagon) holes consume no electrons, we would find that the number of total electrons demanded for bondings, that should be equal to the total number of valence electrons of the system, is nothing but twice the number of triangles.

This electron counting rule also works for the newly predicted most stable boron sheet and nanotube[17, 18], which are composed by triangles and hexagon holes. In those cases, 8 boron atoms form a unit cell, which possess 12 triangles, so according to the above rule, 24 electrons in total are required for bondings, which just corresponds to the 24 valence electrons of 8 boron atoms, giving rise to a bonding balance. As illustrated in Ref. [17], a pure hexagonal boron sheet is prone to accepting electrons, while a pure triangular boron sheet has a surplus of electrons, leading to that a mixture of these two phases with a proper proportion of triangles and hexagons would make the structure more stable. Our electron counting rule may be understood in a similar way. In a boron quasiplanar structure composed by triangles, a hexagon (pentagon) hole could be produced by removing the central atom from a group of six (five) triangles that share the central atom. As discussed above, according to the multi-center deficient-electron bonding scheme, each triangle consumes two electrons, such a removal will reduce one boron atom that has three valence electrons, and therefore twelve (ten) electrons for bondings are cut down simultaneously. In this way, one may change the number of hexagon (pentagon) holes to realize the adjustment of the balance of the supplied and demanded electrons. Consequently, the electron counting rule manifests itself that a proper proportion of hexagon (pentagon) holes and triangles should be kept to give rise to the most stable boron quasiplanar structures. For instance, in B_{80} cluster, the proportion of pentagon holes and triangles is 1/10. Fig. 1(c) shows the valence electronic density of the hexagons in B_{80} cluster. One may see that high electron densities exist around the center boron atoms, showing a ring-like multi-center bonding pattern. As a hexagon with central atom [Fig. 1(c)] can be viewed as a combination of six triangles, the ring-like multi-center bond may be evolved from the combination of six 3c2e bonds.

To seek for stable solid phases of B_{80} , we have attempted sc and fcc crystal structures, and taken two steps to find the optimized structures. In the first step, with the atomic positions in B_{80} clusters fixed, the total energy of B_{80} solid with the presumed lattice, was calculated in every $0.1 \text{ \AA}$ for the lattice constant (where the data with precision of $0.01 \text{ \AA}$ are obtained by a spline interpolation from the calculated data with precision of $0.1 \text{ \AA}$). Without loss of generality, in the calculations a properly fixed orientation of B_{80} molecules is kept, namely, the xy plane of B_{80} molecule is arranged to be along the (100) plane in the sc and fcc structures, which makes the system bear a relatively high symmetry. In order to examine the effect of orientational disorder on the calculated results, we have rotated B_{80} clusters randomly to reduce the symmetrical orientations, and recalculated the optimized lattice parameters and the corresponding total energy. The results show that the total energy increase a lot (several eV per B_{80} cluster), suggesting that our presumed geometrical configuration is energetically more favorable. We therefore get the total energy as a function of lattice parameters for both sc and fcc structures, where a single minimum in the curve of energy versus the lattice constant is found, indicating that a stable structure

may exist. In the second step, on the basis of the structures obtained in the first step, a full relaxation including the atomic positions, cell shape and volume was conducted by means of the BFGS minimization until the forces acting on atoms are less than a tolerance of 10^{-5} Hartree/Bohr. As a result, after relaxation, the shape, lattice parameter, and the total energy are all varied, with the cohesive energies 4.9 eV and 18.2 eV per B_{80} unit, i.e., 0.06 and 0.23 eV/atom, for the sc and fcc B_{80} solids, respectively, which are measured with respect to the isolated B_{80} cluster. As the fcc phase appears to be more stable in energy than the sc phase, we will focus on the fcc phase in the following.

As shown in Fig. 1(d), B_{80} cage is dramatically distorted in fcc solid, where the I_h symmetry of an isolated B_{80} is lowered to T_h symmetry for B_{80} in fcc phase. To check it further, we have relaxed a single distorted B_{80} cage in a supercell, and found that it can indeed revert to the isolated B_{80} cluster [Fig. 1(a)] with a spherical shape. Therefore, the distortion of B_{80} cages in a fcc solid may be mainly owing to the formation of boron-boron chemical bonds between nearest neighbor B_{80} cages. Fig. 1(b) and (e) show the configurations of a pair of hexagons along the z axis before and after distortion, respectively. The sharing arrix of the two neighboring hexagons is elongated (from 1.678 Å to 1.940 Å) and broken, while two central atoms in the hexagons move outward, resulting in a planar rhombus structure composed by atoms denoted by the number 1-4 in Fig. 1(e), where the side length is 1.773 Å and the angle is 57.87° . The rhombus is surrounded by four skew quadrilaterals, two triangles and two pentagons. Due to the symmetry, there are total six such pairs of hexagons along the x , y and z axes in one isolated B_{80} cluster, which evolve into a deformed B_{80} unit with six geometrically equivalent rhombuses. The boron atoms sitting in the centers of the rest eight hexagons in a B_{80} unit all shift inward. Fig. 1(f) presents the valence electron density of the rhombus structure. From the profile, we observe that the boron atoms labeled by 3, 1, 4 and 3, 2, 4 form two B-B-B bridge-type 3c2e bonds, which are very similar to the B-H-B bridge-type 3c2e bond in B_2H_6 . The valence electron density is rather high between every two of the four boron atoms, and an elliptical high-density area presents in the center of the rhombus. It appears that the two B-B-B bridge-type 3c2e bonds are coupled with each other, which eventually become a new complicated four-center bond. It will be illustrated later that the formation of this four-center rhombus is crucial to the bondings between the nearest neighbor B_{80} units.

As can be seen in Figs. 2(a) and (b), there are four boron-boron chemical bonds between every two nearest neighbor B_{80} units. The two green (dark) bonds are formed between two vertical rhombuses, while the two yellow (grey) bonds connect two parallel pentagons. The lengths of the green and yellow bonds are 1.734 Å and 1.700 Å, respectively, both falling into the typical boron-boron bond length scales in B_{80} fullerene [15] and other boron materials. In a fcc B_{80} solid, every B_{80} unit has 12 nearest neighbor B_{80} units, and every two nearest neighbor B_{80} units are bonded by four boron-

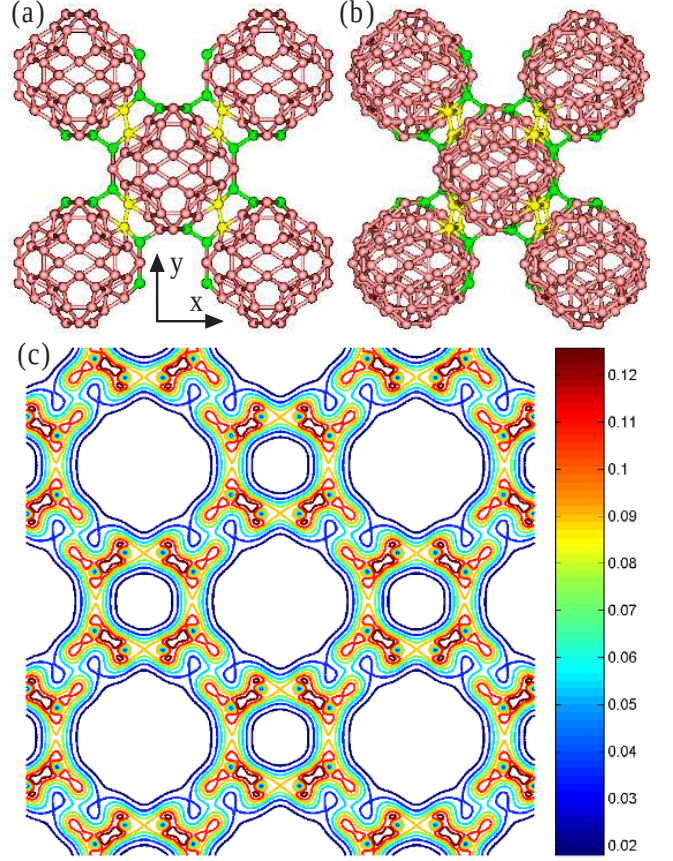


FIG. 2: (Color online) (a) Schematic map of the bondings of the nearest neighboring five B_{80} clusters in (001) plane, the lengths of the green (dark) and yellow (grey) bonds are 1.734 Å and 1.700 Å, respectively; (b) a slightly rotational view of (a), where four boron-boron chemical bonds between the nearest neighbor B_{80} units can be seen clearly; (c) the contour map of valence electron density of the fcc B_{80} solid (a) in the (001) plane through the center of B_{80} units, corresponding to the cross section of (a). The red and blue color represent high and low electron densities, respectively. The unit of color bar is electrons/Bohr³.

boron chemical bonds, 48 bonds are therefore formed between every B_{80} unit and its 12 neighbors. In this sense, the fcc B_{80} solid can be regarded as a three-dimension network of the distorted B_{80} units. Fig. 2(c) presents the valence electron densities of the fcc B_{80} solid in the (001) plane through the center of B_{80} units. The five big circles indicate the inner hollows of the five B_{80} units in Fig. 2(a). It can be observed that there are high electron densities between neighboring cages, indicating stronger interactions between neighboring B_{80} units. In particular, the densities corresponding to the green bonds are rather high, showing a σ -like bond character. (The yellow bonds do not lay in this plane and are not shown directly in the density map.) Thus, we may conclude that B_{80} clusters in the fcc phase are connected by strong B-B σ -like chemical bonds.

In Fig. 2(c), it seems that small spherical-like hollow structures are formed in the space between the neighbor B_{80} units. By looking into it further, we find that it is indeed a B_{24} cage-

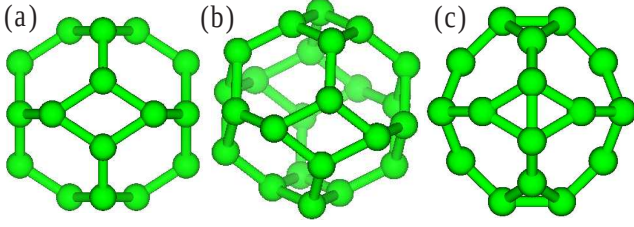


FIG. 3: (Color online) (a) The cage-like B_{24} structure between the neighbor B_{80} units; (b) is the rotational view of (a); (c) is the distorted structure after relaxation in a supercell, where the rhombus breaks into two triangles.

like structure composed of 6 rhombuses and 8 hexagons [Fig. 3(a) and (b)]. This structure could be considered as a distorted truncated octahedron or cubo-octahedron, and interestingly, it is also a regular part of the crystal structure of metal-dodecaborites MB_{12} (M is a metal) [37], in which a metal atom is located at the center of each boron cubo-octahedron. We have also relaxed the B_{24} cage in a supercell, and seen that it is distorted and becomes more spherical, and every rhombus breaks into two triangles [Fig. 3(c)]. The total energy of the relaxed B_{24} cage is 0.57 eV/atom larger than the isolated B_{80} cluster. Thus, this B_{24} cubo-octahedral structure could exist only in a solid, and cannot appear in an isolated form. Similar to the situation of MB_{12} , the interstitial atoms may be inserted into these hollows to form new boron compounds.

As listed in Table I, the total energy of fcc B_{80} solid is 0.23 eV/atom lower than the isolated B_{80} , 0.35 eV/atom higher than α -rhombohedral B_{12} solid. Note that the cohesive energy of the fcc C_{60} solid is about 1.6 eV per C_{60} [24], i.e., 0.03 eV/atom. Furthermore, fcc C_{60} solid and other molecular solids [38, 39, 40] are condensed by van der Waals force, in which no chemical bonds are formed among the neighboring clusters. Our calculations on the inter-cluster bonds, valence electron densities, and the cohesive energies indicate that the condensed mechanism of fcc B_{80} solid is totally different from the above molecular solids.

The energy bands and the density of states (DOS) for the fcc B_{80} solid are calculated with the optimized lattice constants, as presented in Fig. 4. The energy bands are quite dispersive, and several bands spread across the Fermi level, as manifested in the left panel of Fig. 4, showing that the fcc B_{80} solid is a metal. As the most of the BNTs are also observed to have the metallic electronic structures, such a metallic property of the fcc B_{80} solid is conceivable. Unlike the fcc C_{60} solid that is a band insulator with a direct energy gap of 1.5 eV [24],

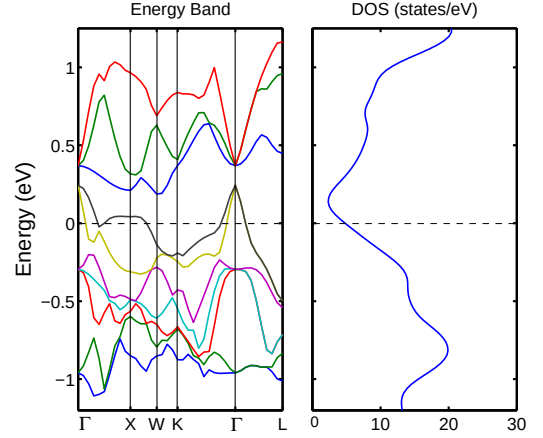


FIG. 4: (Color online) Left panel: Energy bands of the fcc B_{80} crystal. Right panel: Density of states (DOS) of electrons for the fcc B_{80} crystal around the Fermi level, which is obtained by means of a smearing technique. The Fermi level is set to zero.

the present result shows that the energy gap closes when B_{80} clusters condense to form a fcc solid. This is understandable, because there are strong interactions between the neighboring B_{80} clusters in a solid phase, which would inevitably enhance the overlap of the charge densities of electrons, thus broadening the energy bands, and eventually leading to the vanishing of the energy gap. However, albeit the fcc B_{80} solid shows a metallic behavior, the electronic density at the Fermi surface is not so high, as shown in the right panel of Fig. 4, in which the DOS profile is depicted. The DOS has a minimum slightly above the Fermi level, giving rise to a low electronic density of states. Of particular interest is that the DOS profile of the fcc B_{80} around the Fermi level look very similar to that of MgB_2 , in which the DOS of MgB_2 also exhibits a minimum just above the Fermi level [41, 42]. MgB_2 is a well-known two-gap superconductor with transition temperature $T_c \sim 39$ K [43], where it has been established that the energy bands at the Fermi level mainly derive from B orbitals, and is a typical metal that is essentially attributed to metallic boron with covalent B-B and ionic B-Mg bonding [42], whose superconductivity is now well understood within the electron-phonon mechanism. This present analogy between the primary characters of electronic structures of fcc B_{80} and MgB_2 gives a hint that superconductivity might exist in the fcc B_{80} crystal.

In conclusion, in terms of the first-principles DFT calculations, we have found that B_{80} fullerenes can condense to form stable sc and fcc solids. It is also uncovered that B_{80} cages in fcc solid phase are geometrically distorted, where the I_h symmetry is lowered to T_h , and four boron-boron chemical bonds are formed between every two nearest neighbor B_{80} cages. The total energy of B_{80} fcc solid is 0.23 eV/atom lower than the isolated B_{80} fullerene. A simple electron counting rule is proposed, which could explain the stability of B_{80} fullerene and the recently predicted most stable boron sheet. In comparison to the ordinary semiconducting boron crystals that can

TABLE I: Total energies of the boron sheet, isolated B_{80} cluster, and B_{80} fcc solid, with respect to α -rhombohedral boron solid, in eV/atom.

	boron sheet	isolated B_{80}	B_{80} fcc solid
Ref. [17]	0.38	0.56	-
This work	0.46	0.58	0.35

become a metal or superconductor under high pressure, our calculated electronic structures, with some primary features quite similar to those of MgB_2 superconductor, show that the fcc B_{80} solid is a metal at ambient pressure, and may be a candidate of new superconductor. As a result, in spite of the popular phases of α -, β - rhombohedral and tetragonal borons, the fcc B_{80} metal may be another novel form for pure boron in nature.

The authors are grateful to X. Chen, S. S. Gong, and Z. C. Wang for helpful discussions. All of the calculations are completed on the supercomputer NOVASCALE 6800 in Computer NetWork Information Center (Supercomputing Center) of Chinese Academy of Sciences. This work is supported in part by the National Science Foundation of China (Grant Nos. 90403036, 20490210), the National Science Fund for Distinguished Young Scholars of China (Grant No. 10625419), the MOST of China (Grant No. 2006CB601102), and the Chinese Academy of Sciences.

* Author to whom correspondence should be addressed.
Email:gsu@gucas.ac.cn

- [1] H. W. Kroto, J. R. Heath, S. C. O'Brien, R. F. Curl and R. E. Smalley, *Nature* **318**, 162 (1985).
- [2] K. M. Kadish, R. S. Ruoff, Eds., *Fullerene: Chemistry, Physics and Technology* (Wiley, New York, 2002).
- [3] K. C. Buschbeck, *Boron compounds, elemental boron and boron carbides. Gmelin Handbook of Inorganic Chemistry viii, Supplement 2* (Springer, Berlin, 1981).
- [4] F. Perrot, *Phys. Rev. B* **23**, 2004 (1981).
- [5] D. W. Bullett, *J. Phys. C: Solid State Phys.* **15**, 415 (1982).
- [6] M. Terauchi, Y. Kawamata, M. Tanaka, M. Takeda and K. Kimura, *J. Solid State Chem.* **133**, 156 (1997).
- [7] C. Mailhot, J. B. Grant, and A. K. McMahan, *Phys. Rev. B* **42**, 9033 (1990).
- [8] M. I. Eremets, V. V. Struzhkin, H. Mao, and R. J. Hemley, *Science* **293**, 272 (2001).
- [9] Y. Ma, J. S. Tse, D. D. Klug, and R. Ahuja, *Phys. Rev. B* **70**, 214107 (2004).
- [10] I. Boustani and A. Quandt, *Europhys. Lett.* **39**, 527 (1997); *J. Chem. Phys.* **110**, 3176 (1999).
- [11] A. Quandt, A. Y. Liu, and I. Boustani, *Phys. Rev. B* **64**, 125422 (2001); J. Kunstmann and A. Quandt, *ibid.* **74**, 035413 (2006); J. Kunstmann and A. Quandt, *Chem. Phys. Lett.* **402**, 21 (2005).
- [12] M. H. Evans, J. D. Joannopoulos, and S. T. Pantelides, *Phys. Rev. B* **72**, 045434 (2005).
- [13] K. C. Lau, R. Pati, R. Pandey, and A. C. Pineda, *Chem. Phys. Lett.* **418**, 549 (2006).
- [14] I. Cabria, M. J. López and J. A. Alonso, *Nanotechnology*. **17**, 778 (2006).
- [15] N. G. Szewacki, A. Sadrzadeh, and B. I. Yakobson, *Phys. Rev. Lett.* **98**, 166804 (2007).
- [16] N. G. Szewacki, *Nanoscale. Res. Lett.* **3**, 49 (2008).
- [17] H. Tang and S. Ismail-Beigi, *Phys. Rev. Lett.* **99**, 115501 (2007).
- [18] X. Yang, Y. Ding, and J. Ni, *Phys. Rev. B* **77**, 041402(R) (2008).
- [19] P. A. Heiney, J. E. Fischer, A. R. McWhie, W. J. Romanow, A. M. Denenstein, J. P. McCauley Jr., and A. B. Smith, *Phys. Rev. Lett.* **66**, 2911 (1991); J. E. Fischer, P. A. Heiney, A. R. McWhie, W. J. Romanow, A. M. Denenstein, J. P. McCauley Jr., and A. B. Smith, *Science* **252**, 1288 (1991); G. Van Tendeloo, S. Amelinckx, M. A. Verheijen, P. H. M. van Loosdrecht, and G. Meijer, *Phys. Rev. Lett.* **69**, 1065 (1992); etc.
- [20] W. Kratschmer, L. D. Lamb, K. Fostiropoulos and D. R. Huffman, *Nature (London)* **347**, 354 (1990).
- [21] E. D. Jemmis and E. G. Jayasree, *Acc. Chem. Res.* **36**, 816 (2003).
- [22] P. Hohenberg and W. Kohn, *Phys. Rev.* **136**, B864 (1964).
- [23] R. W. Lof, M. A. van Veenendaal, B. Koopmans, H. T. Jonkman, and G. A. Sawatzky, *Phys. Rev. Lett.* **68**, 3924 (1992); E. L. Shirley and S. G. Louie, *ibid.* **71**, 133 (1993); etc.
- [24] S. Saito and A. Oshiyama, *Phys. Rev. Lett.* **66**, 2637 (1991).
- [25] The ABINIT code is a common project of the Universite Catholique de Lovain, Corning Incorporated, and other contributors (<http://www.abinit.org>).
- [26] S. Goedecker, *SIAM J. Sci. Comput.* **18**, 1605 (1997).
- [27] M. C. Payne, M. P. Teter, D. C. Allan, T. A. Arias and J. D. Joannopoulos, *Rev. Mod. Phys.* **64**, 1045 (1992).
- [28] X. Gonze, *Phys. Rev. B* **54**, 4383 (1996).
- [29] X. Gonze, *Phys. Rev. B* **55**, 10337 (1997).
- [30] X. Gonze, C. Lee, *Phys. Rev. B* **55**, 10355 (1997).
- [31] N. Troullier and J. L. Martins, *Phys. Rev. B* **43**, 1993 (1991).
- [32] M. Fuchs and M. Scheffler, *Comput. Phys. Commun.* **119**, 67 (1999).
- [33] J.P. Perdew, Y. Wang, *Phys. Rev. B* **45**, 13244 (1992).
- [34] W. Kohn and L. J. Sham, *Phys. Rev.* **140**, A1133 (1965).
- [35] J. D. Head and M. C. Zerner, *Chem. Phys. Lett.* **122**, 264-270 (1985).
- [36] P. J. Durrant and B. Durrant, *Introduction to Advanced Inorganic Chemistry* (Wiley, New York, 1962).
- [37] E. L. Muetterties, Eds. *The chemistry of boron and its compounds* (Wiley, New York, 1967).
- [38] Q. B. Yan, Q. R. Zheng, G. Su, *Phys. Rev. B* **73**, 165417 (2006).
- [39] Q. B. Yan, Q. R. Zheng, G. Su, *J. Phys. Chem. C* **111**, 549 (2007).
- [40] S. C. Erwin and W. E. Pickett, *Science*, **254**, 842 (1991).
- [41] P. P. Singh, cond-mat/0104580.
- [42] J. Kortus, I. I. Mazin, K. D. Belashchenko, V. P. Antropov, and L. L. Boyer, *Phys. Rev. Lett.* **86**, 4656 (2001); J. M. An and W. E. Pickett, *ibid.* **86**, 4366 (2001).
- [43] J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani and J. Akimitsu, *Nature* **410**, 63 (2001).